
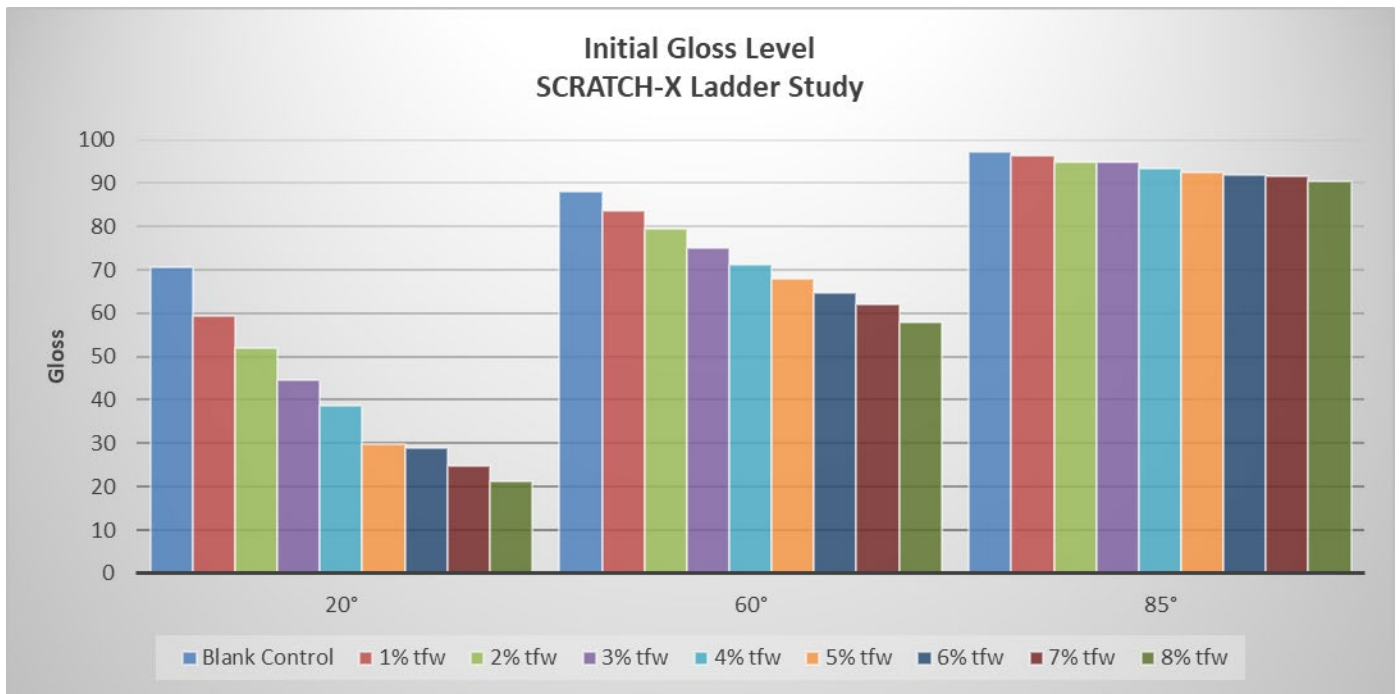


## Water-based Clear Urethane Modified-Acrylic Floor Lacquer with HALOX® SCRATCH-X

	<u>Supplier</u>	<u>lbs/100 gal</u>	<u>% wt</u>	<u>Formula Properties</u>	
Water		88.9	10.06	% Solids/wt	36.21
Dowanol DPM	Dow Chemical	65.37	7.40	% Solids/vol	32.03
Dowanol DPnB	Dow Chemical	28.00	3.17	PVC	3.56
Ammonium Hydroxide (28%)		2.54	0.29	VOC g/l	243.54
Byk 346	BYK	2.54	0.29	Density lbs/gal	8.84
Byk 028	BYK	2.54	0.29		
NeoPac R-9045	DSM Coating Resins	644.62	72.93		
<b>HALOX® SCRATCH-X</b>	<b>ICL\Phosphate Specialty</b>	<b>43.92</b>	<b>4.97</b>		
Foamstar SI 2292	BASF	3.51	0.40		
Acrysol RM-8W	Dow Chemical	2.00	0.23		
<b>TOTAL</b>		<b>883.94</b>	<b>100</b>		

DISCLAIMER: The information in this document (including any graphics, recommendations, or other materials) and any materials made available through this document are provided "as is" and without any warranties of any kind, either express or implied. All information presented in these materials should be independently verified by the users of these materials. To the fullest extent permissible by applicable law, ICL Specialty Products Inc. for itself and its subsidiaries and affiliates ("ICL") expressly disclaims all warranties of merchantability, fitness for a particular purpose, title and non-infringement of any nature or kind. Furthermore, ICL does not warrant or make any representations regarding the use or the results of any use of the materials in this document, terms of its correctness, accuracy, reliability, or otherwise. Information herein may include technical inaccuracies or typographical errors and may be inaccurate or become inaccurate as a result of development occurring after the printing of these materials. ICL accepts no obligation to verify or maintain the accuracy of such information, nor to ensure such updates are brought to the user's attention. User assumes all risk associated with reliance of these materials.

## Water-based Clear Urethane Modified-Acrylic Floor Lacquer with HALOX® SCRATCH-X

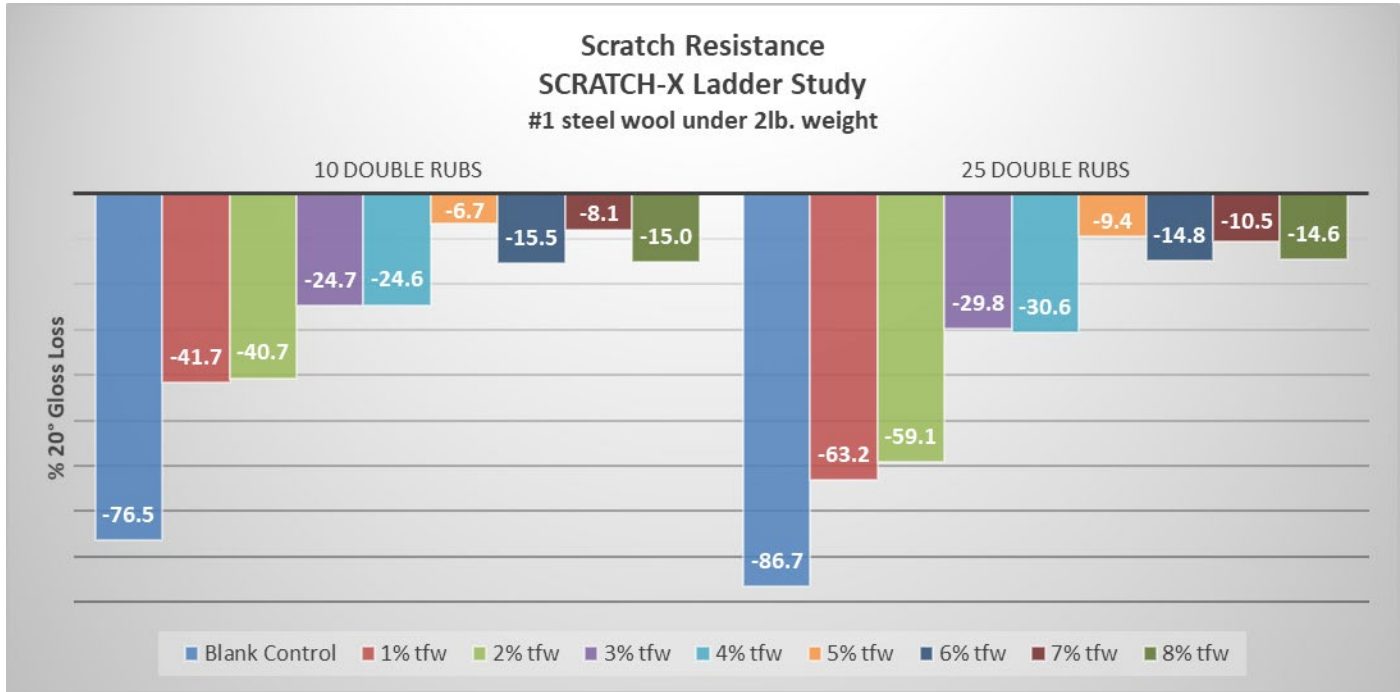

DISCLAIMER: The information in this document (including any graphics, recommendations, or other materials) and any materials made available through this document are provided "as is" and without any warranties of any kind, either express or implied. All information presented in these materials should be independently verified by the users of these materials. To the fullest extent permissible by applicable law, ICL Specialty Products Inc. for itself and its subsidiaries and affiliates ("ICL") expressly disclaims all warranties of merchantability, fitness for a particular purpose, title and non-infringement of any nature or kind. Furthermore, ICL does not warrant or make any representations regarding the use or the results of any use of the materials in this document, terms of its correctness, accuracy, reliability, or otherwise. Information herein may include technical inaccuracies or typographical errors and may be inaccurate or become inaccurate as a result of development occurring after the printing of these materials. ICL accepts no obligation to verify or maintain the accuracy of such information, nor to ensure such updates are brought to the user's attention. User assumes all risk associated with reliance of these materials.